


RESEARCH REPORT SERIES no. 122-2011

# COMPARISON OF CLAY WITH FLINTS FROM SILBURY HILL AND LOCAL NEOLITHIC POTTERY FABRICS

Harriet White and Matthew Canti

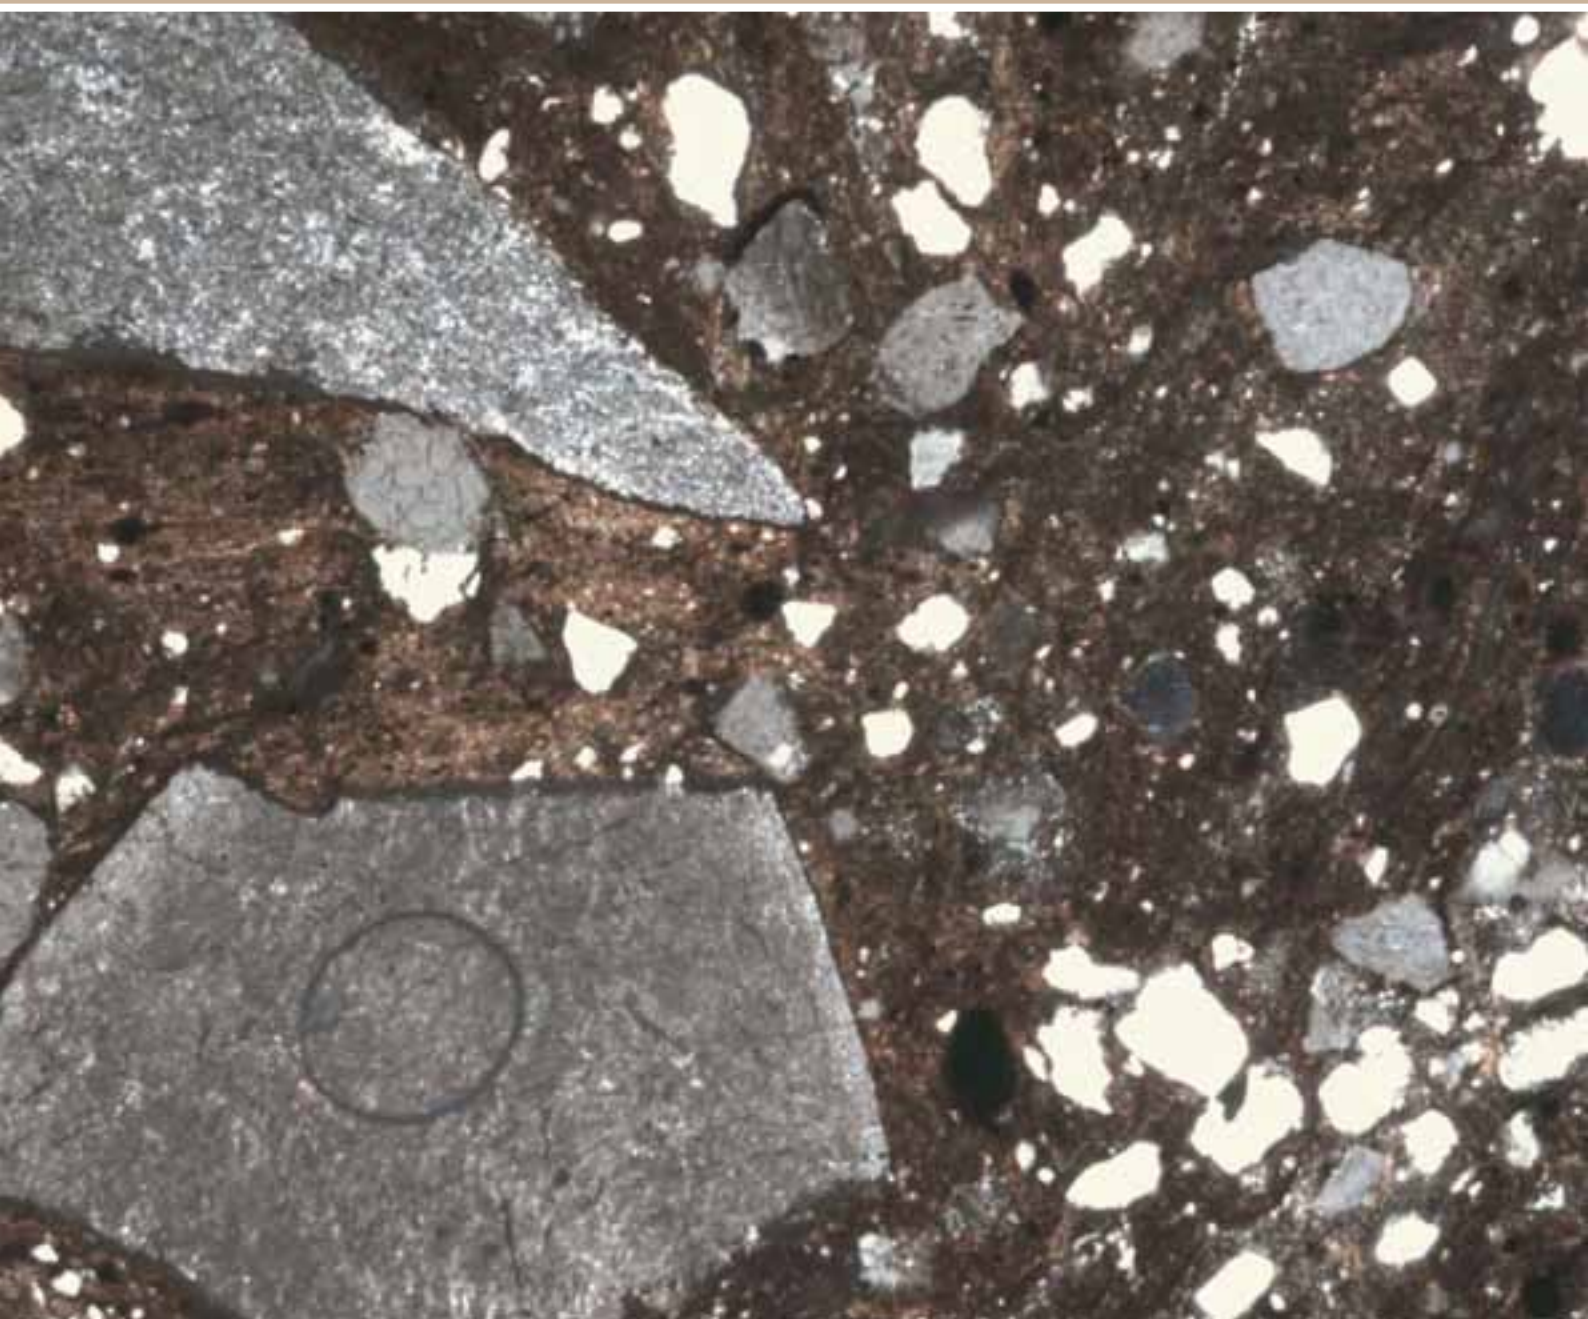

INTERVENTION  
AND ANALYSIS



ENGLISH HERITAGE

*This report has been prepared for use on the internet and the images within it have been down-sampled to optimise downloading and printing speeds.*

*Please note that as a result of this down-sampling the images are not of the highest quality and some of the fine detail may be lost. Any person wishing to obtain a high resolution copy of this report should refer to the ordering information on the following page.*

## **Comparison of clay with flints from Silbury Hill and local Neolithic pottery fabrics**

Harriet White and Matthew Canti

NGR: SU 1001 6853

© English Heritage

ISSN 2046-9799 (Print)

ISSN 2046-9802 (Online)

*The Research Report Series incorporates reports by the expert teams within the Investigation & Analysis Division of the Heritage Protection Department of English Heritage, alongside contributions from other parts of the organisation. It replaces the former Centre for Archaeology Reports Series, the Archaeological Investigation Report Series, the Architectural Investigation Report Series, and the Research Department Report Series.*

*Many of the Research Reports are of an interim nature and serve to make available the results of specialist investigations in advance of full publication. They are not usually subject to external refereeing, and their conclusions may sometimes have to be modified in the light of information not available at the time of the investigation. Where no final project report is available, readers must consult the author before citing these reports in any publication. Opinions expressed in Research Reports are those of the author(s) and are not necessarily those of English Heritage.*

*Requests for further hard copies, after the initial print run, can be made by emailing:*

*Res.reports@english-heritage.org.uk*

*or by writing to:*

*English Heritage, Fort Cumberland, Fort Cumberland Road, Eastney, Portsmouth PO4 9LD*

*Please note that a charge will be made to cover printing and postage.*

## SUMMARY

The excavations at Silbury Hill in 2007-2008 raised questions concerning the truncated nature of the old ground surface (Canti, 2011), leading to a consideration of whether clay had been removed to make ceramics. This study investigates whether or not the Silbury Hill clay-with-flints was a potential raw material for Neolithic ceramic manufacture, by comparing modern clay-with-flints and thin-sectioned examples of suitable local pottery.

The results demonstrate that some coarse flint-containing fabrics were manufactured from naturally gritty clays. Although a direct link cannot be made between the Silbury clay and local ceramic examples, it could, nevertheless, have been a viable material for pottery manufacture.

## CONTACT DETAILS

Harriet White, Institute of Archaeology, 31-34 Gordon Sq., London WC1H 0PY  
Matthew Canti, English Heritage, Fort Cumberland Eastney PO4 9LD, UK

## CONTENTS

|                                     |   |
|-------------------------------------|---|
| Introduction .....                  | 1 |
| Sample Material .....               | 1 |
| Results .....                       | 1 |
| Comparative Neolithic Pottery ..... | 2 |
| Discussion.....                     | 4 |
| Bibliography.....                   | 5 |

## Introduction

During the excavations at Silbury Hill in 2007-2008, questions concerning the truncated nature of the old land surface (Canti 2011) led initially to a consideration of whether material had been removed, at the time of the Hill's construction, to be used for some practical purpose. An obvious possibility would be that the clay could be used to make ceramics. The aim of this petrographic study, therefore, is to investigate whether or not the Silbury Hill clay-with-flints was a potential raw material for Neolithic ceramic manufacture.

## Sample Material

The material analysed comprised clay-with-flints from beneath Silbury Hill made into briquettes after removal of the >2mm fraction, then fired to 700°C, 800°C, 900°C and 1000°C, each receiving dwell times of 30 minutes and 1 hour at the top temperature. The briquettes were then prepared as standard thin sections.

Thin sections from Neolithic pottery of Peterborough and Windmill Hill types recovered from excavations in Wiltshire, and held in archive at the Department of Archaeology, University of Southampton were made available for comparison. In addition, thin sections of Grooved Ware from Durrington Walls (DW07) were kindly lent from the Alan Vince collection (held by APS, Heckington, Lincs.)

## Method

The ceramic thin sections were examined at magnifications of 25x to 400x under a polarizing light microscope and the fabrics characterised following Whitbread's (1995, 379-388) thin section descriptive system.

## Results


### *Silbury Hill clay-with-flints*

The Silbury Hill clay-with-flints is characterised petrographically by its coarse fraction (>100µm, and occupying about 10% of the total field) containing predominant angular to sub-rounded fine sand to very coarse sand-sized flint (Figures 1 and 2). The flint fragments are grey under crossed polars (XPL) and colourless to yellow in plane polarised light (PPL). Few sub-rounded grains of fine to medium sand-sized monocrystalline quartz, and sub-angular to sub-rounded fine to coarse sand-sized iron oxide inclusions, very rare to absent sub-rounded medium to coarse sand-sized grains of chalcedonic quartz, and angular fine sand-sized calcite are also present in the coarse fraction. The fine fraction (<100µm, and occupying about 10% of the total field) comprises predominant sub-angular to sub-rounded monocrystalline quartz, rare white mica and very rare to absent sub-angular feldspars (plagioclase and microcline). The Silbury Hill clay-with-flints contains




clay pellets (about 2% of the total field). The clay pellets are rounded and up to 1.25mm in size, have high optical density and are dark red brown in XPL and dark brown to black in PPL. They may contain conchoidal fractures and monocrystalline quartz silt.

The colour and optical activity of the Silbury Hill clay-with-flints micromass is dependent on firing temperature and dwell time. Fired from 700 °C, 30 minutes dwell time to 900 °C, 30 minutes dwell time the micromass is slightly optically active, orange red in XPL and yellow brown in PPL (Figure 1). From 900 °C, 60 minutes dwell time to 1000 °C, 60 minutes dwell time the micromass is optically inactive, red brown in XPL and brown in PPL (Figure 2).

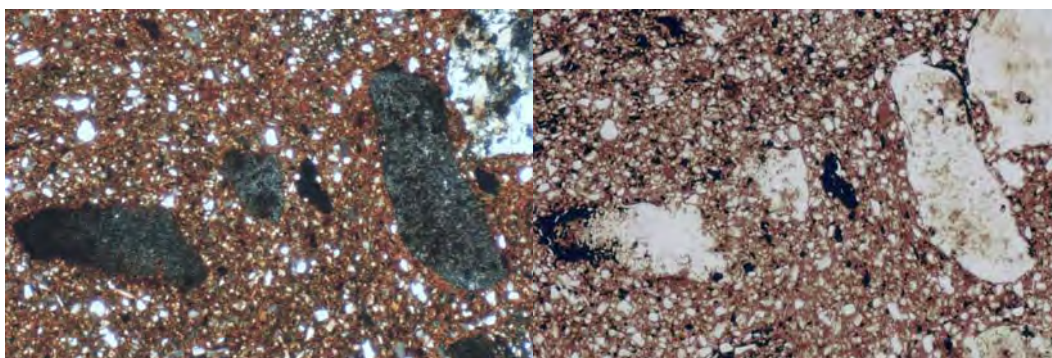

*Figure 1: Thin section photomicrographs of Silbury Hill clay-with-flints, fired at 700°C for 30 minutes. Left image is taken in XPL and right image is taken in PPL. Showing sub-angular flint inclusions (grey) and chalcedonic quartz (top right). Width of image is 2.8mm.*

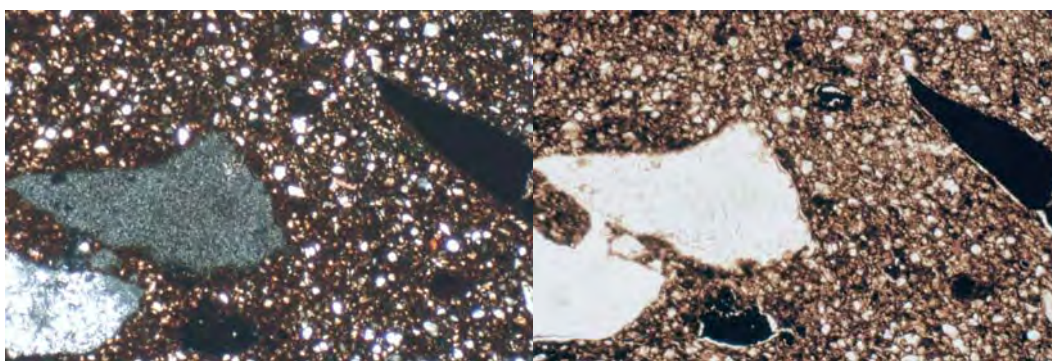

*Figure 2: Thin section photomicrographs of Silbury Hill clay-with-flints, fired at 1000°C for 30 minutes. Left image is taken in XPL and right image is taken in PPL. Showing angular flint inclusions (grey in XPL), and iron oxide inclusions (black in XPL and PPL). Width of image is 2.8mm.*


## Comparative Neolithic Pottery

None of the Grooved Ware from Durrington could have been made from Silbury clay-with-flints, nor could the majority (ca. 50 different samples) of the Wiltshire Windmill Hill and Peterborough Wares examined. However, a small number of ceramic fabrics from


Avebury and its environs show similar petrographic attributes. These fabrics are described below:-

*Fabric 1: Samples NI60 (Windmill Hill Ware), Avebury and NI84 (Peterborough Ware), West Overton*

The micromass is optically active, yellow brown in XPL and yellow brown in PPL. Inclusions occupy approximately 20% of the total field. The coarse fraction ( $>100\mu\text{m}$ ) comprises predominant medium to very coarse sand-sized, angular to sub-rounded flint and very few fine sand-sized sub-rounded quartz and flint. The flint is colourless to pale brown in PPL. The fine fraction ( $<100\mu\text{m}$ ) comprises silt to very fine sand-sized quartz and rare white mica. Rounded clay pellets occupy about 1% of the total field. These have high optical density, are red brown in XPL, dark red brown in PPL, and are up to 0.7mm in size (Figure 3).

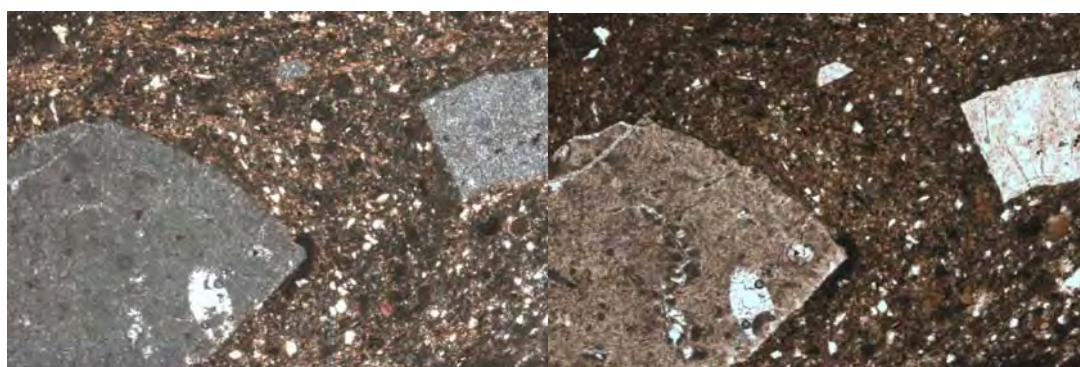

*Figure 3: Thin section photomicrographs of Fabric 1, Sample NI60 (Windmill Hill Ware). Left image is taken in XPL and right image is taken in PPL. Showing angular flint inclusions (grey) in a silt and very fine sand-sized quartz matrix, similar to the Silbury Hill clay-with-flints (Figures 1 and 2). Width of image is 2.8mm.*

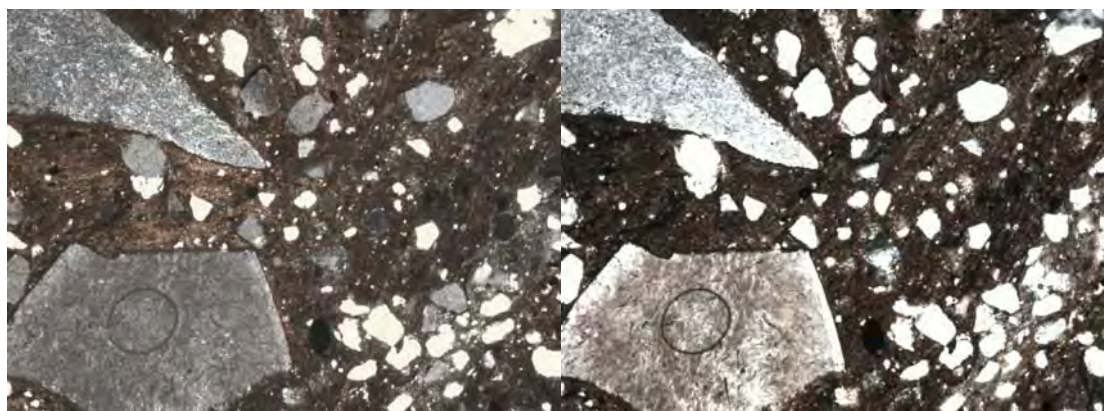

*Figure 4: Thin section photomicrographs of Fabric 2, Sample NI61 (Peterborough Ware). Left image is taken in XPL and right image is taken in PPL. Showing angular flint inclusions (grey) in a silt to sand-sized quartz matrix. Width of image is 2.8mm.*



*Fabric 2: Samples N159 (Windmill Hill Ware) and N161 (Peterborough Ware), Avebury*

The micromass is optically slightly active, red brown in XPL and brown in PPL. Inclusions occupy about 30% of the total field and the coarse fraction ( $>100\mu\text{m}$ , approximately 25% of the total field) is composed of predominant medium sand-sized sub-rounded quartz, and few medium sand to granular-sized grains of angular to sub-angular flint. The flint is pale yellow to brown in PPL. The distribution of the quartz inclusions is heterogeneous, with grains closed (bottom right, Figure 4) to open-spaced (top right, Figure 4). The fine fraction ( $<100\mu\text{m}$ , approximately 5% of the total field) comprises silt-sized quartz and very rare black iron oxide nodules. Textural concentration features are present ( $< 2\%$  of the total field) as rounded to distorted clay pellets.

## Discussion

Flint-containing Neolithic pottery is commonly thought of as being 'flint-tempered', that is, the coarse flint inclusions were intentionally added by the potter to enhance clay workability, or the physical properties of the finished pot (for example Cleal 1995, 187). It is interesting to note that the Silbury Hill clay-with-flints has petrographic features in common with the examples of Windmill Hill and Peterborough Wares from West Overton (Fabric 1). Most notably, the fired clay and ceramic fabric both feature coarse, sub-angular inclusions of flint in a fine quartz-rich matrix, with rare white mica and clay pellets. Though there are variations that indicate a different source clay for the pottery (for example, coarse iron oxide inclusions are present in the clay-with-flints, but absent in the ceramic fabric), the findings do suggest the ceramic fabric may have been prepared using the naturally gritty, flint-containing clay, rather than being flint-tempered. This link between clay-with-flints and Neolithic pottery manufacture has previously been made with regard to Windmill Hill Ware, recovered from the site of Windmill Hill, where ceramic fabrics were related to clay-with-flints from the Marlborough Downs (Hodges 1965, 43-44 and Plates XVI a-c).

While Fabric 2 also has similar mineralogical attributes to the Silbury Hill clay-with-flints, such as coarse flint in a quartz-rich matrix, with quartz silt and iron oxide nodules contained in the fine fraction, the apparent bimodal grain-size distribution (medium sand to granule-sized flint in a medium sand-sized quartz matrix) is indicative the clay was tempered.

The results of this petrographic analysis demonstrate that while some coarse flint-containing fabrics were manufactured by tempering the clay (Fabric 2), it also appears to be the case that naturally gritty clays were exploited for pottery manufacture (Fabric 1). While a direct link cannot be made between the Silbury Hill clay-with-flints and Fabric 1, due to some variation in the coarse and fine fractions, the Silbury Hill clay-with-flints would have been a viable clay source for pottery manufacture.

## Bibliography

Canti, M G 2011 *Geoarchaeological Analysis from Silbury Hill Excavations 2007/2008*. Research Department Report 58/2011

Cleal, R M 1995 'Pottery fabrics in Wessex in the fourth to second millennia BC', in Kinnes, I and Varndell, G (eds) *Unbaked Urns of Rudely Shape: Essays on British and Irish Pottery for Ian Longworth*. Oxbow Monograph 55, 185-194

Hodges, H 1965 'Thin sections of sherds from Windmill Hill', in Smith, I (ed) *Windmill Hill and Avebury: Excavations by Keiller, 1925-1939*. Oxford: Clarendon Press, 43-44

Whitbread, I K 1995 *Greek Transport Amphorae: A Petrological and Archaeological Study*. Fitch Laboratory Occasional Paper 4, Exeter: The Short Run Press



## ENGLISH HERITAGE RESEARCH AND THE HISTORIC ENVIRONMENT

English Heritage undertakes and commissions research into the historic environment, and the issues that affect its condition and survival, in order to provide the understanding necessary for informed policy and decision making, for the protection and sustainable management of the resource, and to promote the widest access, appreciation and enjoyment of our heritage. Much of this work is conceived and implemented in the context of the National Heritage Protection Plan. For more information on the NHPP please go to <http://www.english-heritage.org.uk/professional/protection/national-heritage-protection-plan/>.

The Heritage Protection Department provides English Heritage with this capacity in the fields of building history, archaeology, archaeological science, imaging and visualisation, landscape history, and remote sensing. It brings together four teams with complementary investigative, analytical and technical skills to provide integrated applied research expertise across the range of the historic environment. These are:

- \* Intervention and Analysis (including Archaeology Projects, Archives, Environmental Studies, Archaeological Conservation and Technology, and Scientific Dating)
- \* Assessment (including Archaeological and Architectural Investigation, the Blue Plaques Team and the Survey of London)
- \* Imaging and Visualisation (including Technical Survey, Graphics and Photography)
- \* Remote Sensing (including Mapping, Photogrammetry and Geophysics)

The Heritage Protection Department undertakes a wide range of investigative and analytical projects, and provides quality assurance and management support for externally-commissioned research. We aim for innovative work of the highest quality which will set agendas and standards for the historic environment sector. In support of this, and to build capacity and promote best practice in the sector, we also publish guidance and provide advice and training. We support community engagement and build this in to our projects and programmes wherever possible.

We make the results of our work available through the Research Report Series, and through journal publications and monographs. Our newsletter *Research News*, which appears twice a year, aims to keep our partners within and outside English Heritage up-to-date with our projects and activities.

A full list of Research Reports, with abstracts and information on how to obtain copies, may be found on [www.english-heritage.org.uk/researchreports](http://www.english-heritage.org.uk/researchreports)

*For further information visit [www.english-heritage.org.uk](http://www.english-heritage.org.uk)*

